AB INITIO NANOSPIN

Journées Nationales en Nanosciences et en Nanotechnologies (J3N)

Ab initio Simulation of Transport in Nanospintronics

M. Alouani[1], O. Bengone[1], S. Lebègue[2], X. Feng[1], Xi Chen[1], S. Javaid[1], L. Debbichi[1], J. Aguiar[1], H. Dreyssé[1]
[1] Institut de Physique et Chimie des Matériaux de Strasbourg, UMR 7504, 23 rue du Loess, BP43, 67034 Strasbourg, France
[2] Laboratoire de Cristallographie et de Modélisation des Matériaux Minéreaux et Biologiques (LCM3B),UMR 7036, Vandoeuvre-les-Nancy, France

AB INITIO NANOSPIN

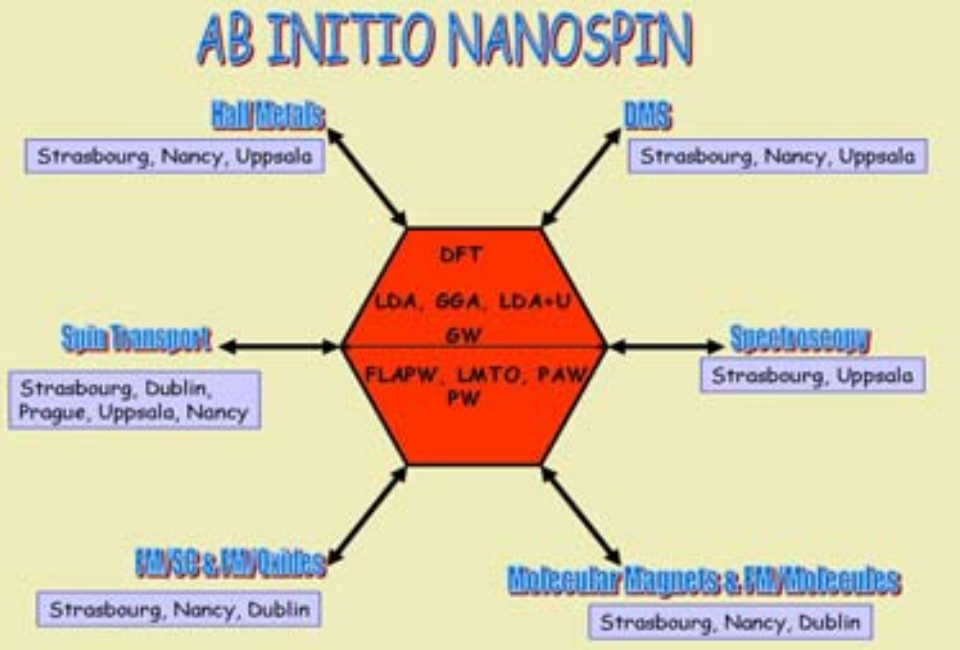

Magnetic moments and IEC

The magnetic moments increase at the Interface and magnetic moments are Induced in the MgO spacer.



Exponential decrease of the IEC with the spacer size. The parallel alignment remains the ground-state magnetic configuration

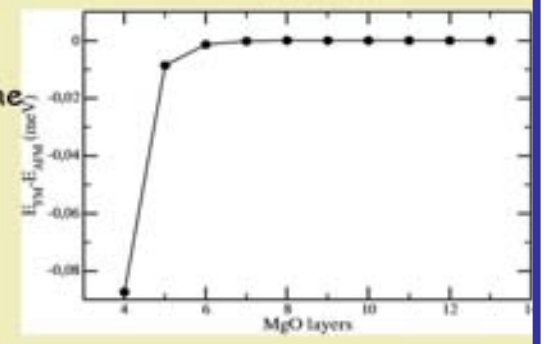

Conclusions:

1. IEC favor parallel alignment of the magnetization at the interfaces of Fe/MgO/Fe
2. The calculated TMR values are higher than experiment -> Atomic relaxations have a strong effect on the TMR
3. Adding vanadium at the Fe interface acts as an extra barrier reducing the TMR, and its different magnetic states can change it considerably
4. The double barriers Fe/V/Fe/MgO/Fe offers many possibilities to change the TMR as a function of the different magnetic states.

Perspectives:

- Extend this study to molecular spacers
- Use half-metals (like SFMO) or DMS as leads
- Transport with finite bias (non-equilibrium Green's function formalism)

Geant Magneto-Resistance (GMR) mechanism (spin dependant currents)

Spin-up and spin-down currents

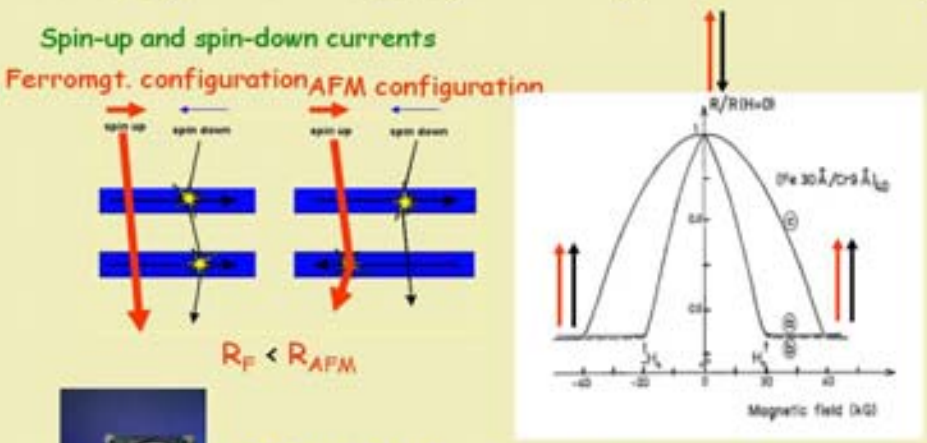

Gb hard drive

M. N. Balbich *et al.*, PRL *61* (1988).
G. Binasch *et al.*, PRB 39 (1989)

Relaxation effect on the magnetic and transport properties of Fe/MgO/Fe junctions

Case	DFT	d_{-4}	d_{-3}	d_{-2}	d_{-1}	d_0	d_1	d_2	d_3
I	unrelaxed	1.433	1.433	1.433	1.433	2.16	2.026	2.026	2.026
II	LSDA	1.297	1.313	1.343	1.120	2.002	2.130	2.119	2.119
III	GGA	1.380	1.414	1.427	1.350	2.219	2.199	2.177	2.185

Atomic relaxations along the junction direction in Å. The d_i are the inter plane distances (d_0 is the distance between Fe and MgO layers).



Charge transfer at the interface calculated using Bader analysis.



Calculated magnetic moments and occupations at the Fe/MgO interface.

Molecular Electronics

Current through a single molecule between electrodes

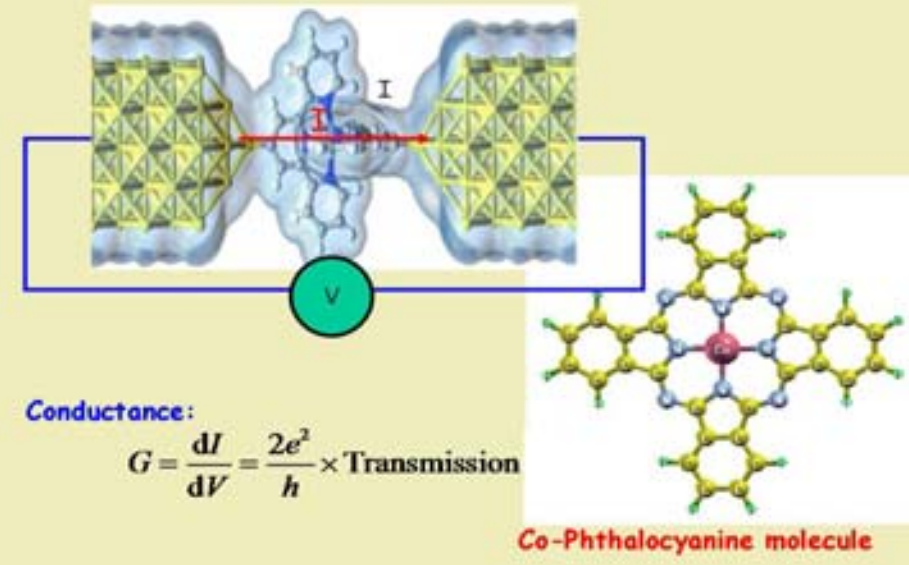

Conductance:

$$G = \frac{dI}{dV} = \frac{2e^2}{h} \times \text{Transmission}$$

Co-Phthalocyanine molecule

Spacer

The use of an amorphous spacer like Al_2O_3 gives a TMR ratio of at most 70%.
Calculated TMR for MgO spacers of the order of 1000% , much higher than the experimental values (240%)
It seems that a better interface leads to a high TMR ratios.
For GaAs and MgO the small lattice misfit makes layer by layer growth possible.
Experimentally, a perfect interface is always complicated.
For Fe/GaAs/Fe, the so called dead magnetic layer of iron at the interface reduces the TMR ratio.
For Fe/MgO/ Fe, the presence of FeO layer at the interface destroys the TMR.

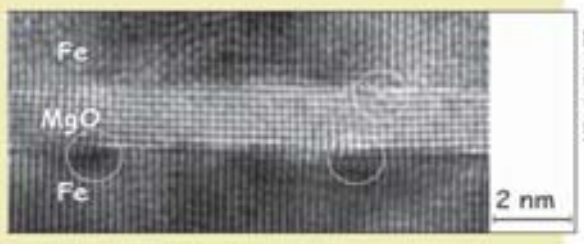

Yuasa et al, Nature Mat. 3, 868 (2004)



Effects of the atomic relaxation on the DOS, the transmission coefficient and TMR



Atomic relaxation effects on the DOS of the Fe atoms at the interface.



Relaxation effects on k-resolved DOS of interface Fe.



Atomic relaxation effects on the transmission coefficient. The colors are the same as for the DOS.

	G_P	G_{AP}	TMR
unrelaxed	1.21×10^{-7}	7.18×10^{-8}	173
LSDA relax.	7.32×10^{-6}	6.74×10^{-7}	9.86
GGA relax.	2.38×10^{-6}	3.23×10^{-8}	72.7
Expt.	-	-	2.47

Atomic relaxation effects on the TMR of $Fe/(MgO)_n/Fe$

X. Feng *et al*, PRB 79, 174 414 (09).

Mn-Pc on Co(001) and Cu(001) surfaces: A total energy calculation

Total energy vs. MnPc distance to the Cu(001) and Co (001) surfaces



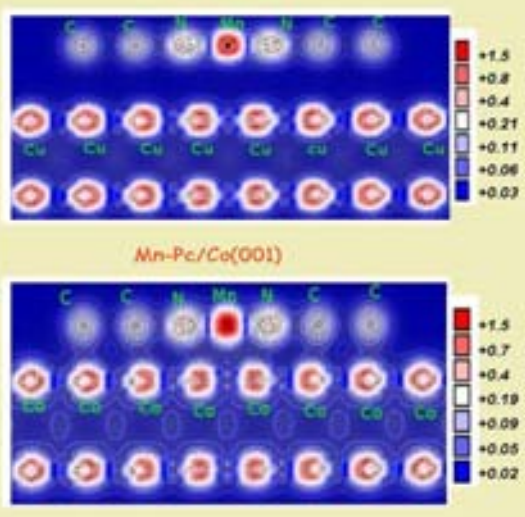

In collaboration with the experimental group of E. Beaurepaire (see Spinorga poster)

Materials-Specific Quantum Transport Codes in Development

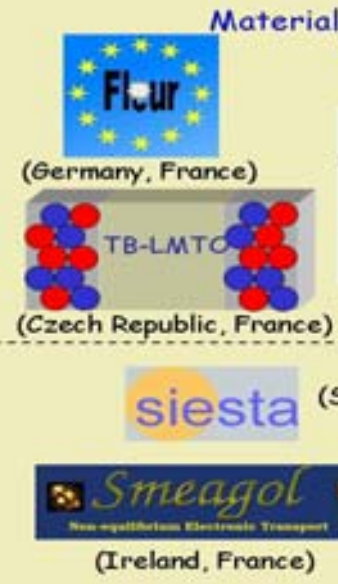

Magnetic-tunnel junction



Molecular-tunnel junction



Magnetic configuration of vanadium layers in Fe/V/MgO/Fe magnetic junction and its effect on the transport properties.



Stable (black) and instable magnetic configuration of $Fe/V_n/(MgO)_m/Fe$ magnetic junctions.



Transmission coefficient of $Fe/V_n/(MgO)_m/Fe$ magnetic junctions for different values of n.
P: Black curve (LE majority) and blue triangles (LE minority).
AP: Green with squares curve (LE majority), and blue triangles (LE minority).

X. Feng *et al*, PRB 79, 214 432 (09).

Co-Phthalocyanine on Cu(111) or Co(111)



Different high symmetry positions hollow (green), bridge (red) and top (blue)



Total energy vs. Molecule-substrate distance.



Co-Pc on Co(111) prefers bridge position



Co-Pc on Cu(111) prefers hollow position

Band structure of Fe and MgO.

The Δ_1 band of Fe and the Δ_1 of MgO conductance bands have the smallest energy difference compared to Δ_5 and $\Delta_{2'}$



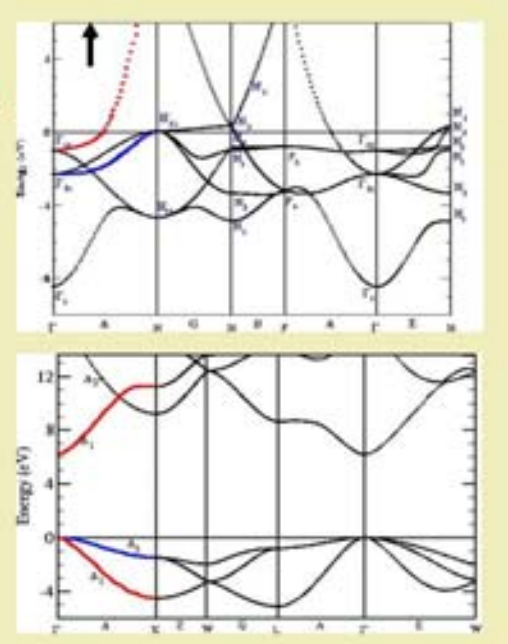

Conductance and TMR of Fe/V/Fe/MgO/Fe magnetic junctions

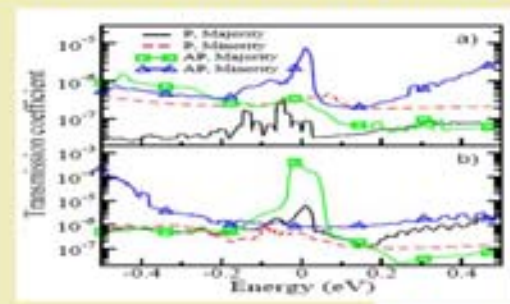

Transmission of Fe/V/Fe/MgO/Fe magnetic junction for the Fe layer near MgO parallel and antiparallel to left iron electrode.

MTJ	Magnet.	Majority G	Minority G	Opt. TMR	Pess. TMR
n = 2, m = 4	↑↑↑	4.78×10^{-8}	3.19×10^{-9}	-0.93	-12
	↑↑↓	3.06×10^{-7}	4.65×10^{-8}		
	↑↑↑	4.50×10^{-8}	4.49×10^{-9}	-0.98	-60
	↑↑↓	3.02×10^{-8}	8.41×10^{-9}		
n = 2, m = 6	↑↑↑	4.62×10^{-9}	5.66×10^{-8}	115	0.99
	↑↑↓	9.89×10^{-11}	3.89×10^{-8}		
n = 4, m = 6	↑↑↑	1.60×10^{-8}	4.49×10^{-8}	49	0.98
	↑↑↓	5.85×10^{-8}	3.14×10^{-8}		

Conductance (in units of e2/h) and TMR of $Fe/V_n/Fe_m/MgO/Fe$. The arrows indicate the magnetizations of the left, middle and right iron layers.

Calculated STM images of Co-Pc on Co(111) or Cu(111)

Expt. A.F. Takacs et al., PRB 78, 233404 (08).



Co-Pc/Co(111) E= 0.9 eV



Co-Pc/Cu(111) E= 0.4 eV

Ministère de l'Enseignement Supérieur et de la Recherche — Agence Nationale de la Recherche ANR — PNANO — NanoSciences — DGA — cea — SFP — cnrs — INSA Toulouse — Université Paul Sabatier Toulouse III — Mairie de Toulouse